

DRAFT UGANDA STANDARD

Second Edition
2018-mm-dd

Hot dip galvanized plain and corrugated steel sheets – Specification

PUBLIC REVIEW DRAFT



Reference number
DUS DEAS 11: 2018

Compliance with this standard does not, of itself confer immunity from legal obligations

A Uganda Standard does not purport to include all necessary provisions of a contract. Users are responsible for its correct application

© UNBS 2018

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilised in any form or by any means, electronic or mechanical, including photocopying and microfilm, without prior written permission from UNBS.

Requests for permission to reproduce this document should be addressed to

The Executive Director
Uganda National Bureau of Standards
P.O. Box 6329
Kampala
Uganda
Tel: +256 417 333 250/1/2
Fax: +256 414 286 123
E-mail: info@unbs.go.ug
Web: www.unbs.go.ug

National foreword

Uganda National Bureau of Standards (UNBS) is a parastatal under the Ministry of Trade, Industry and Cooperatives established under Cap 327, of the Laws of Uganda, as amended. UNBS is mandated to co-ordinate the elaboration of standards and is

- (a) a member of International Organisation for Standardisation (ISO) and
- (b) a contact point for the WHO/FAO Codex Alimentarius Commission on Food Standards, and
- (c) the National Enquiry Point on TBT Agreement of the World Trade Organisation (WTO).

The work of preparing Uganda Standards is carried out through Technical Committees. A Technical Committee is established to deliberate on standards in a given field or area and consists of representatives of consumers, traders, academicians, manufacturers, government and other stakeholders.

Draft Uganda Standards adopted by the Technical Committee are widely circulated to stakeholders and the general public for comments. The committee reviews the comments before recommending the draft standards for approval and declaration as Uganda Standards by the National Standards Council.

This Draft Uganda Standard, DUS DEAS 11:2018, *Hot dip galvanized plain and corrugated steel sheets – Specification*, is identical with and has been reproduced from an East African Standard, EAS 11:2018, *Hot dip galvanized plain and corrugated steel sheets – Specification*, and is being proposed for adoption as a Uganda Standard.

This standard was developed by Mechanical engineering and metallurgy Standards Technical Committee (UNBS/TC 4).

This second edition cancels and replaces the first edition (US EAS 11:2013), which has been technically revised.

Wherever the words, "East African Standard " appear, they should be replaced by "Uganda Standard."



DRAFT EAST AFRICAN STANDARD

DEAS 11 – Hot dip galvanized plain and corrugated steel sheets – Specification

PUBLIC REVIEW DRAFT

EAST AFRICAN COMMUNITY

Copyright notice

This EAC document is copyright-protected by EAC. While the reproduction of this document by participants in the EAC standards development process is permitted without prior permission from EAC, neither this document nor any extract from it may be reproduced, stored or transmitted in any form for any other purpose without prior written permission from EAC.

Requests for permission to reproduce this document for the purpose of selling it should be addressed as shown below or to EAC's member body in the country of the requester:

© East African Community 2013 — All rights reserved
East African Community
P.O.Box 1096
Arusha
Tanzania
Tel: 255 27 2504253/8
Fax: 255 27 2504481/2504255
E-mail: eac@eachq.org
Web: www.eac-quality.net

Reproduction for sales purposes may be subject to royalty payments or a licensing agreement.
Violators may be persecuted

PUBLIC REVIEW DRAFT

Foreword

Development of the East African Standards has been necessitated by the need for harmonizing requirements governing quality of products and services in the East African Community. It is envisaged that through harmonized standardization, trade barriers that are encountered when goods and services are exchanged within the Community will be removed.

In order to achieve this objective, the Community established an East African Standards Committee mandated to develop and issue East African Standards.

The Committee is composed of representatives of the National Standards Bodies in Partner States, together with the representatives from the private sectors and consumer organizations. Draft East African Standards are circulated to stakeholders through the National Standards Bodies in the Partner States. The comments received are discussed and incorporated before finalization of standards, in accordance with the procedures of the Community.

East African Standards are subject to review, to keep pace with technological advances. Users of the East African Standards are therefore expected to ensure that they always have the latest versions of the standards they are implementing.

CD/TZ/8:2016 was prepared by Technical Committee EASC/TC 035 *TC Steel and Steel Products*

PUBLIC REVIEW DRAFT

Galvanized plain and corrugated steel sheets – Specification

1. Scope

This East Africa Draft Standard specifies requirements, test methods and sampling for galvanized plain and corrugated steel sheets for roofing, cladding, fencing, fabrication and general use.

This East Africa Draft Standard does not cover all the special purpose profiles.

2. Normative References

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the reference document (including any amendments) applies.

EAS 196, High strength low – alloy carbon steel for hot rolled and cold rolled sheet - specification

3. Definitions

For the purposes of this East Africa Draft Standard, the following definitions shall apply:

3.1 Galvanized sheets

Steel sheets with a uniform coating of zinc applied by the hot-dip process

3.2 Corrugated sheets

Galvanized steel sheets which are mechanically formed to obtain regular, sinusoidal, profiles, as shown in figure 1

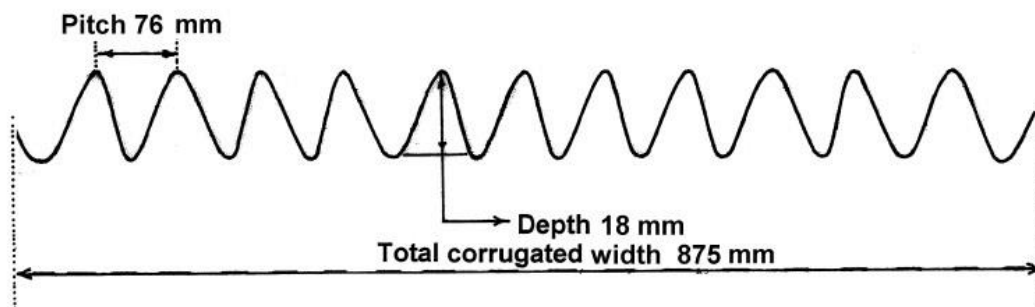


Figure 1 — Profile of corrugated sheets

3.3 thickness

thickness of the base metal.

3.4 Plain

The flat or even sheets without any relief forms

3.5 Pitch

The distance between two corresponding and consecutive points on the corrugated steel sheets along its width

4. General requirements

4.1 Dimensions

4.1.1. Length

When measured in accordance with 9.2.2, the length of sheets shall be as specified in Table 3

4.1.2 Width

The width of plain and corrugated galvanized sheets when measured in accordance with 9.2.4 shall be as specified in Table 2.

4.1.3 Thickness

The thickness of galvanized plain and corrugated sheets shall be expressed in gauges. The corresponding thickness in millimetres shall be as specified in Table 1.

4.1.4 Squareness

When measured in accordance with 9.2.3, the distance between diagonally opposite corners of the sheet shall not differ by more than 10 mm.

4.2 Profile

4.2.1 Depth

The depth of corrugations shall be 18 mm \pm 1.5 mm, when measured in accordance with 9.2.6.

4.2.2 Pitch

The pitch of the corrugations shall be 76 mm \pm 2 mm when measured in accordance with 9.2.5.

4.3 Tensile strength

The tensile strength of plain and corrugated galvanized sheets when determined in accordance with 9.2.7 shall be not less than 300 N/mm. The yield strength shall be not less than 210 N/mm

4.4 Hardness The hardness properties of the steel sheets shall be as follows:
For 32G and 30G sheets to be full hard and for 28G and above sheets to be full hard or half hard

4.5 Resistance to bending

When tested in accordance with 9.2.8, the sheet shall not crack, flatter or splinter.

4.6 Freedom from defects

The sheets shall be uniform, clean and free from defects that would adversely affect their use.

4.7 Finish

The finish on plain and corrugated galvanized sheets shall be 'Mill Finish'.

Table 1 — Base metal thickness of plain and corrugated sheets

Gauge	Thickness (mm)	Tolerance (\pm %)
32	0.20	5
30	0.25	5
28	0.32	5
26	0.40	5
24	0.50	5
22	0.63	5
20	0.80	5
18	1.00	5
16	1.20	5
14	1.50	5
12	2.00	5
10	2.60	5

NOTE: Gauge 32 sheets, should be clearly marked "not for roofing"

Table 2 — Nominal width of plain and corrugated sheets

Width of plain sheets and sheets before corrugation ± 5 %	Number of corrugations	Total corrugated width ± 2.5 %
1220	14	1100
1150	13	1025
1070	12	950
1000	11	875
914	10	800
845	9	725
762	8	645

Table 3 — Nominal length of plain and corrugated sheets

Nominal length, mm + 0.5 %, -0 %	
Plain sheets	Corrugated sheets
2 000	2 000

2 500	2 500
3 000	3 000

5. Galvanized processes (criteria of compliance)

5.1 General requirement

The steel sheets shall be manufactured in accordance with accepted current practice and shall be from rolled milled steel made by a suitable process and meeting the requirements of EAS 196. The sheets shall be true to size and homogenous, with no trace of discontinuity of the zinc coating. They shall also be free from holes, tears, twists, cambers and damaged edges and corners. Corrugations shall be parallel to the edges of the sheets.

5.2 Zinc coating

5.2.1 Zinc coating shall be carried out by the hot-dip process with smelter containing not less than 98.5 % pure zinc. The minimum mass of zinc coating on the two sides of sheet and the corresponding thickness of zinc coating on each side shall comply with the classification specified in Table 4.

5.2.2 The nominal mass of zinc coating per square meter, when tested according to methods specified in 8.1, shall correspond to the classification specified in table 4. The minimum values determined by the methods specified in 8.1, shall be as shown in table 4.

5.2.3 Zinc coating adherence shall be such that there shall be no flaking or splintering in the finished galvanized plain or corrugated sheet, when tested in accordance with 8.2.

5.3 Classification of zinc coating

Galvanized plain and corrugated steel sheets shall be classified into seven (7) classes depending on the mass of zinc coating applied to meet different service and environmental conditions. The classes shall be as specified in table 4.

Table 4 — Classification of galvanized plain and corrugated steel sheet

Coating class	Nominal mass on two sides g/m ²	Minimum mass on two sides by weight method g/m ²	Minimum mass on two sides by antimony chloride method g/m ²	Nominal corresponding thickness on each side µm	Minimum corresponding thickness on each side µm
Z	515	412	360	35	25
Y	450	360	315	31	22
X	387	310	270	26	19
A	305	244	214	21	15
B	244	198	183	17	13
C	214	172	146	15	10
D	183	137	122	13	9

6. Marking

6.1 Conforming sheets

6.1.1 Marking

Each galvanized plain or corrugated steel sheet conforming to this East Africa Draft Standard shall be permanently and indelibly marked with the following:

- a) Manufacturer's name and/or trade mark.
- b) The base metal thickness expressed in gauge with word "GAUGE" in full and millimeter.
- c) The coating class of sheet
- d) The batch identification.
- e) Gauge 32 sheets, should be clearly marked "**not for roofing**" font size 12mm width in every 1m along the length.

6.1.2 Packing

Sheets shall be packed in bundles as shown in the table below

Gauge, G	32			30			28			26		
Length(m)	2	2.5	3	2	2.5	3	2	2.5	3	2	2.5	3
Number of sheet				23	19	16	18	14	12			

6.2 Non-conforming sheets

All non-complying sheets shall be identified by cutting off all four corners at least by 75 mm along the edges diagonally and shall be marked "Rejected" with indelible ink.

7. Sampling

7.1 General

The sampling procedures in 7.2 and 7.3 shall be applied in determining whether a lot complies with the relevant requirements of the specification.

The samples so taken shall be deemed to represent the lot.

7.2 Sample for inspection and dimensional test

7.2.1 From the lot, random sampling shall be done in accordance with Table 5.

7.2.2 For the manufacturing industry, three sheets shall be taken in every 8 h shift.

7.3 Sample for other tests

From the sample taken in accordance with 7.2.1, take at random one sheet.

Table 5 — Sampling plan

Number of sheets	Sample for inspection and dimensional tests, number of sheets
1 - 16	1
17- 48	2
49 -100	3
101- 160	4
161 - 200	5
Over 200	5 per 200 sheets

8. Testing for zinc coating

8.1 Mass of zinc coating

8.1.1 Weight method

The steel sheets are weighed before galvanizing. They shall be then passed through the galvanizing process and weighed again at the end of the process.

NOTE – The Antimony Chloride Method will be used as the criteria for compliance and not the weight method.

8.1.2 Antimony chloride method

The test piece of minimum area 5 000 mm² shall be weighed and then introduced into a zinc-stripping solution of one part antimony chloride and twenty parts hydrochloric acid (specific gravity 1.19), and shall remain therein until the coating has completely dissolved. The test piece shall be taken out of the solution when the violent chemical reaction ceases, rinsed in running water, brushed to remove any loose substance, dried and weighed.

8.1.3 Calculation

The average of the gain or loss in mass (grams) calculated from the results obtained from three test pieces shall represent the mass of zinc coating on both sides of each test piece (see Annex A).

The results shall be expressed in grams per square metre (g/m²).

8.2 Coating adherence test

The test shall consist of subjecting the test piece to deformation by bending in one direction. The test piece shall either be bent mechanically or gripped in hand-operated device (mandrels may also be used) and bent until the two legs of the test piece are parallel to each other, i.e. through 180°.

A second test piece shall be bent in the opposite direction.

The sheets shall be bent round a diameter of 38 mm.

9. Inspection and physical tests

9.1 Inspection

Inspect the sample taken in accordance with 6 for compliance with 4.6 and 5.1.

9.2 Dimensions

9.2.1 Thickness

Measure to the nearest 0.01 mm the thickness of each sheet in the sample of the sheets at any point at least 10 mm from an edge and end of the sheet.

9.2.2 Length

Place each sheet in the sample in turn on a flat rigid surface. Measure to the nearest 1 mm the length of each sheet along the centre line of the sheet.

9.2.3 Square-ness

Place each sheet in the sample in turn on a flat rigid surface. Measure to the nearest 1 mm the distance between the diagonally opposite corners of each sheet and record to the nearest mm the difference between the two measurements.

9.2.4 Width

9.2.4.1 Plain sheets

Place each sheet in the sample in turn on a rigid surface. Measure to the nearest 1 mm across the width of the sheet

9.2.4.2 Corrugated sheets

Place each of the sheets in the sample in turn on a flat rigid surface and measure to the nearest 1 mm across the width of the sheet. Choose at random a cross-section of the sheet and if, because of the springy nature of the sheet, the underside of the downwards corrugations or troughs are not all in contact with the supporting surface, apply sufficient pressure to the upper surface of the sheet to bring the lower surface into full contact with the supporting surface. Ensure that the application of pressure causes no deformation of the sheet other than that needed to bring the corrugations into contact with the rigid surface.

Place the width gauge appropriate to the type of sheet being tested across the sheet at any chosen cross-section and at right angle to the sides of the sheet and adjust the gauge to fit firmly over the outermost corrugations. Determine whether the width of the sheet complies with the requirements of table 2. Both edges of the corrugated sheet shall be turned upwards while measuring

9.2.5 Pitch

With the sheet in contact with a flat surface, place a transparent graduated rule on edge across the sheet so that it rests perpendicularly on the crests of two adjoining corrugations far from the points of contact, and read the distance between them to the nearest 1 mm. Repeat the process to improve your results by taking the average of five readings for the distance between several crests.

NOTE. Any other appropriate method may be used to measure the pitch

9.2.6 Depth of corrugations

With the initial rule lying flat across the corrugations at the edge of the sheet, use another graduated rule or calipers to measure the perpendicular distance between the initial rule and the rigid support.

NOTE. Any other appropriate method may be used to measure the pitch

9.2.7 Tensile strength

From the sample in Clause 7, prepare a tensile test specimen, after stripping off coating, by cutting a strip 30 mm x 80 mm, such that the length of the specimen is transverse to the direction or rolling of the sheet. The portion of sheet from which the test piece is cut shall be carefully flattened. Determine the tensile strength of the specimen..

If the tensile strength of the test specimen fails the requirements of 4.3, prepare two further test specimens and determine their tensile strength. If both specimens comply with the requirements, discard the results of the first specimen, but if either of the additional specimens fails to meet the requirements, deem the sheet and the lot to be defective

9.2.8 Bend test and coating adherence test

A test specimen shall be selected in accordance with Clause 7 and shall be prepared to measure 10 mm in width and 120 mm in length.

It shall be cut with its length transverse to the direction of rolling of the sheet. Carefully bend the strip round a drum of diameter 38 mm (mandrels may also be used) until the edges of the specimen are approximately semi-circular..

If the specimen cracks, prepare and test two further specimens in the same way. If both these test specimens comply with the requirements of 4.4, 4.5 and 5.2.3, discard the results obtained on the first specimen, but if either of the two cracks at the bend, deem the sheet and lot to be defective.

9.2.9 Hardness test

The hardness test of the steel sheets shall be in accordance to ISO 6507-1:2018

Annex A

Reference method for determination of the zinc coating mass

A.1 Principle

Using a specimen with a surface area of at least 5 000 mm², the loss of mass in grams when the coating is dissolved, multiplied by 200, will represent the coating mass in grams per square meter of the product (for both sides).

NOTE – To verify the mass of coating, three specimens shall be cut and tested, one from the mid-width position and one from each side, no closer than 25 mm from the side edge of a sample piece approximately 300 mm in length on the coated width

A.2 Reagent and preparation of the solution

A.2.1 Reagent

Hydrochloric acid (HCL = 1.19 g/cm³)
Antimony tri-chloride

A.2.2 Preparation of the solution

This prepared solution permits the execution of numerous successive dissolutions under satisfactory conditions of attack of the coating, both from the point of view of speed and accuracy.

A.3 Apparatus

Balance, capable of weighing samples to an accuracy of 0.01 g. For the test, use a take-off device.

A.4 Procedure

The following operations are applied to each sample:

- a) If necessary, degrease the sample with an organic solvent, which will not attack the coating, then dry the sample;
- b) Weigh the sample to an accuracy of 0.01 g;
- c) Place the sample in the hydrochloric acid solution with hexamethylenetetramine or antimony chloride inhibitor at an ambient temperature of 20 °C to 25 °C leave the sample immersed in the solution until the release of hydrogen ceases or only a few bubbles are released;
- d) After the attack, wash the sample and brush under running water, dry with a cloth and then by heating to around 100 °C and cool or dry by blowing with warm air;
- e) Weigh the sample again to an accuracy of 0.01 g;
- f) Determine the difference between the mass of the coated sample and that of the sample without its coating. This difference, calculated in grams, represents the mass (m) of the coating.

A.5 Calculation

The coating weight shall be obtained from the following formulas. Method 1 shall be the reference method in case of a dispute:

$$\text{Method 1} \quad C_1 = \frac{W_1 - W_2}{A} \times 10^6$$

$$\text{Method 2} \quad C_2 = \frac{W_1 - W_2}{W_2} \times t \times 7850$$

Where

C is zinc coating in g/m²;

A is area of test specimen (length x width);

W_1 is weight (g) of test piece before stripping;

W_2 is weight (g) of test piece after stripping (base metal);

t is thickness (mm) of test piece after stripping (base metal);

10^6 is conversion factor W is in g, t in mm, while C is in g/m²

7850 is density of steel, kg/m³

NOTE – Method 1 shall be used for regular pieces of specimen (either square or rectangular). In case where it's difficult to cut regular test pieces, e.g. the heavier sheet gauges, method 2 shall be used.